

NASA-CR-191949

P

1/14/2

## ABSTRACT ASRM PROCESS DEVELOPMENT IN AQUEOUS CLEANING

**BILL SWISHER - AEROJET ASRM DIVISION**  
**1 NASA DRIVE, IUKA, MS 38852**  
**PHONE: (601) 423-0855**

IN-20-CR

8 DECEMBER 1992

JULY 1992

Process development in aqueous cleaning is taking place at the Aerojet Advanced Solid Rocket Motor (ASRM) Division under a NASA Marshall Space and Flight Center contract for design, development, test and evaluation of the ASRM including new production facilities. Lockheed Missiles and Space Company and Aerojet have formed a team partnership. Lockheed, as prime contractor, is providing systems engineering and integration and facility construction with overall responsibility and accountability for the project. Aerojet, as a subcontractor, is heading the propulsion design, development, and manufacturing of the new booster. The ASRM will utilize aqueous cleaning in several manufacturing process steps to clean case segments, nozzle metal components, and igniter closures. ASRM manufacturing process development is underway, including agent selection, agent characterization, subscale process optimization, bonding verification, and scale-up validation.

After a literature search and screening demonstrations of 11 aqueous cleaning agents, three agents (Turco 3878 LF-NC, Daraclean 283, and Blue Gold) were chosen for cleaning ability demonstrations. As a result, Turco 3878 LF-NC has been selected for further process testing. Process parameters are currently being tested for optimization utilizing a Taguchi Matrix, including agent concentration, cleaning solution temperature, agitation and immersion time, rinse water amount and temperature, and use/non-use of drying air.

Based on results of process development testing to date, several observations are offered:

- Aqueous cleaning appears effective for steels and Sermetel-coated metals in ASRM processing.
- Aqueous cleaning agents may stain and/or attack bare aluminum metals to various extents. Effects have not been characterized.
- Aqueous cleaning appears unsuitable for thermal sprayed aluminum-coated steel.
- Aqueous cleaning appears to adequately remove a wide range of contaminants from flat metal surfaces, but supplementary assistance may be needed to remove clumps of tenacious contaminants embedded in holes, etc.
- Hot rinse water appears to be beneficial to aid in drying of bare steel and retarding oxidation rate.

In summary, process development in aqueous cleaning for the ASRM Project is progressing satisfactorily. An agent has been selected and subscale process optimization is in progress. Aqueous cleaning has been demonstrated at the lab scale to be an effective alternative to vapor degreasing. The Aerojet ASRM Division and the entire ASRM Team are committed to successful activation of full-scale aqueous cleaning processes.

(NASA-CR-191949) ASRM PROCESS  
DEVELOPMENT IN AQUEOUS CLEANING  
(Lockheed Missiles and Space Co.)

26 p

N93-21355

Unclass



GENCORP  
AEROJET  
ASRM Division

# ASRM Process Development In Aqueous Cleaning

Bill Swisher  
December 8, 1992



GENCORP  
AERONET  
ASRM Division

Aqueous Cleaning Development

## Overview

- Purpose And Logic
- Cleaning Agent Selection
- Process Optimization



GENCORP  
AÉROJET  
ASRM Division

*Purpose And Logic*

## ASRM Aqueous Cleaning

- Case Segments
  - HP9Ni-4Co-0.3C Steel
- Nozzle
  - D6AC Steel
  - Coatings TSA Or Semmetel 64-1
- Igniter Closure
  - HP9Ni-4Co-0.3C Steel



GENCORP  
AERONET  
ASRM Division

# Yellow Creek

*Purpose And Logic*






**GENCORP  
AÉROJET  
ASRM Division**

# **Facility**

***Purpose And Logic***

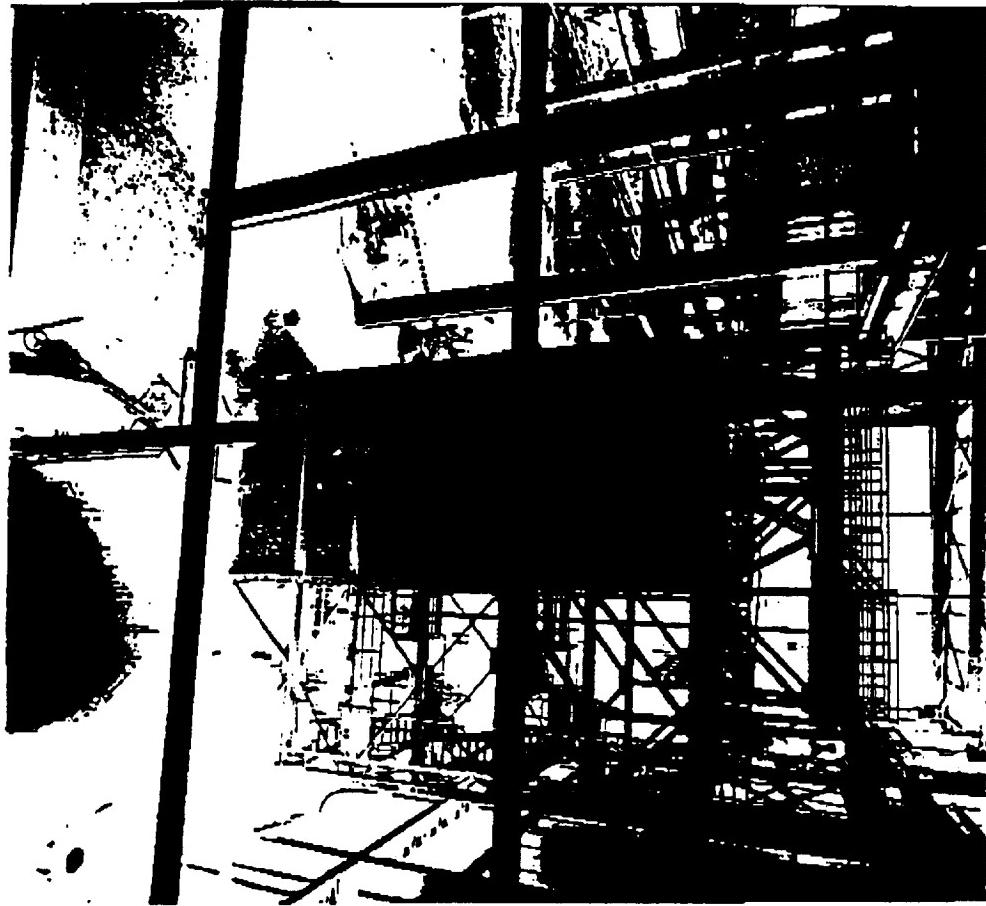




GENCORP  
AÉROJET  
ASRM Division

# ASRM

*Purpose And Logic*

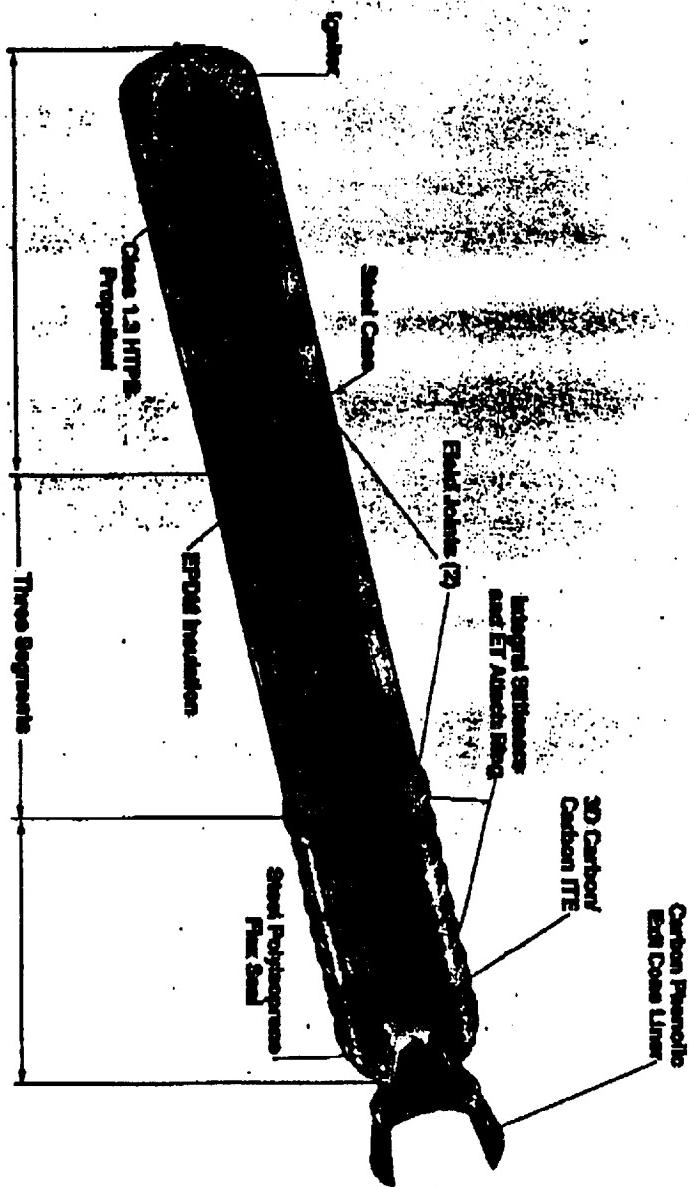



**ENCORP  
AÉROJET  
ASRM Division**

# ASRM Cleaning Processes Flow

## IGNITER — NOZZLE

**NEW  
FIRE  
NOZZLES**

**KSC Motor**  
**Dismantling**  
**Initial Measure**

**SSC Motor**  
**Dismantling**

<b>Truck</b>	<b>Barge</b>
<b>To</b>	<b>To</b>
<b>YC</b>	<b>YC</b>
<b>(ECCS)</b>	
	<b>Slag Weigh</b>
	<b>Char Measure</b>
	<b>Incul Measure</b>

**KSC Removal  
SAC Removal**

**KSC Removal  
SSC Removal**

	Truck To YC	Truck To YC (VCD)
Posttest/Flight Evaluation		

```

graph TD
    A[Insert Helicollie] --> B[Aqueous Clean]
    B --> C[Washout & Rough Clean]
    C --> D[Plastic Media Blast]
    D --> E[Remove Tunnel Floor Plates,  
IET-A Fittings & Cable Brackets]
    E --> F[Weigh]
    
```

**Waterjet  
Tardown  
CLOSURE ONLY:  
Waterjet  
Media Blast  
Aqueous Clean**

**Waterjet**  
**Lardown**  
**Waterjet**  
**Media Blast**  
**Aquous Clean**

**EMAT & Eddy Current Inspect**

**Hydrotest**

**EMAT & Eddy Current inspect**

**Dimensional Inspect**

**Remove Helicolls**

**Zirconium Silicate Media Blast**

**Aqueous Clean**

*Truck  
To  
APD  
(VCI)*

<b>EMAT &amp; Eddy Current</b>
<b>Hydrotest (Fixed Housing Only)</b>
<b>EMAT &amp; Eddy Current</b>
<b>Dimensional Inspect</b>
<b>Aqueous Clean</b>

**Pass Through Airlocks  
To OSEE & Paint**

Huck 10  
*Counting Vandals*  
ACKNOWLEDGMENTS

1

Purpose And Logic






**GENCORP  
AEROMAT  
ASRM Division**

**Purpose And Logic**

# Development Testing Logic

## ASRM Manufacturing Process Development Specification TM05528

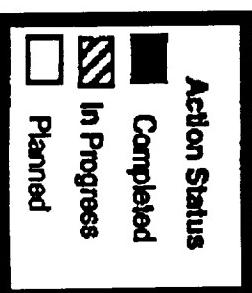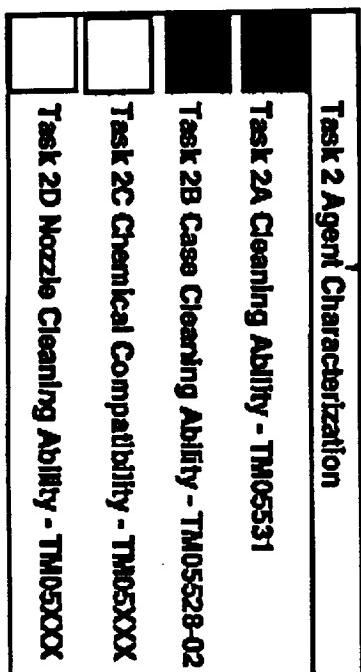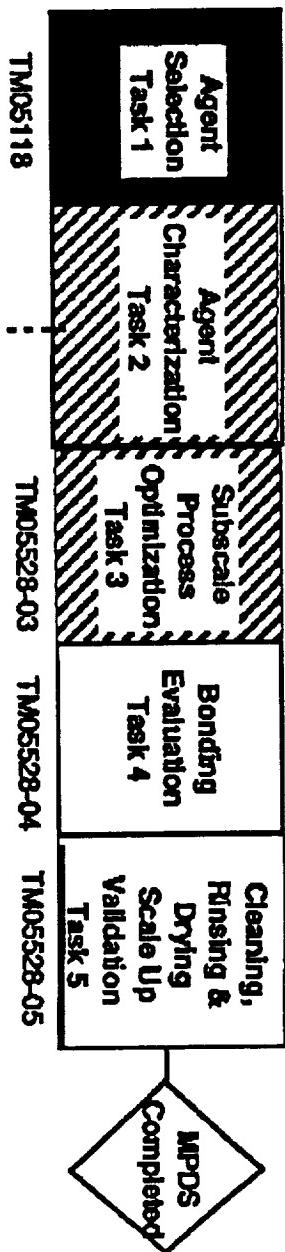



GENCORP  
AÉROJET  
ASRM Division

## *Agent Selection*

# Task 1 - Screening Demonstration Test

- Literature Search Inconclusive
- Eleven Candidates Tested For Corrosion And Bonding Effects With D6AC and HP9-4-30 Steel
  - Turco 3878 LF-NC
  - Daraclean 282
  - Brulin 815GD
  - Cortec 419
  - Turco 6778
  - Duraclean 283
  - HurriSafe Special
  - Blue Gold
  - Turco 4215
  - Gillite 0650
  - HurriSafe Heavy Duty
- Cleanliness And Compatibility Comparison
  - CONSCAN Readings At 2 Hours And 24 Hours (Storage In Nitrogen)
- Bond In Tension Comparison
  - Steel - Chenlok - EPDM Insulation
- Goal To Select Three Agents For Further Testing



GENCORP  
AÉROJET  
ASRM Division

## Task 1 - Screening Demonstration Test (Cont'd)

# Results

- No Candidate Agent Performed Definitively Above Others

- No Adverse Corrosion Or Compatibility Reactions
- None Caused Lowered CONSCAN Readings
- Bond Strengths Similar

- Three Agents Selected

- Turco 3878 LF-NC (Turco, Inc.)
- Emulsion Cleaning History By Aerojet Propulsion Division
- Daraclean 283 (W.R. Grace Co.)
  - History Cleaning Small Parts In Industry
- Blue Gold (Modern Chemical Co.)
  - Emulsion Cleaning History By Martin Marietta Space Vehicle Division



GENCORP  
AEROLET  
ASRM Division

*Agent Selection*

## Task 2A - Cleaning Ability Test

- Three Agents Tested For Down Selection
  - Turco 3878 LF-NC
  - Daraclean 283
  - Blue Gold
- Several Basis Metals Tested
  - HP9-4-.30, TSA 4130 Steel, And SermeTel 7075-T73 Aluminum
- Data Collected:
  - Residual Species Analysis (HP9-4-.30)
  - Compatibility Characterization Of Coated Materials
  - Cleaning Ability Demonstration (All)
  - Bonding Demonstration (HP9-4-.30)



GENCORP  
AÉROJET  
ASRM Division

*Task 2A - Cleaning Ability Test (Cont'd)*

## Residual Species Analysis

- Purpose: To Demonstrate If Residual Species Remain On Cleaned Metal Surface

- Results:

Agent	Particulate	NVR
-------	-------------	-----

No Agent (Control)	.5	.6
--------------------	----	----

Turco 3878 LF-NC	.3	.2
------------------	----	----

Daraclean 283	.6	.2
---------------	----	----

Blue Gold	0.0	.1
-----------	-----	----

- All Three Removed Particulate And Provided Cleaner Base Metal Surface Than Media Blast



ENCORP  
AÉROJET  
ASRM Division

### Task 2A - Cleaning Ability Test (Cont'd)

## Compatibility Characterization

- Purpose: To Demonstrate Effect Of Cleaning Solutions On Nozzle Metals

- Results:

Agent	<u>TSIA Steel</u>	<u>SermeTel Aluminum</u>	<u>*Aluminum</u>
Turco 3878	-No Foaming	-No Reaction	-Lightly Tarnished
LF-NC	- Mild Staining Of Surface		
	- Least Rust Color Under Surface Coat		
Blue Gold	- Moderate Foaming	-No Reaction	-Moderately Tarnished
	-Moderate Staining Of Surface		
	- Rust Color Under Surface Coat		
Daraclean 283	- Heavy Foaming	-No Reaction	-Heavily Tarnished (Blackened)
	-Heavy Staining Of Surface		
	-Most Rust Color Under Surface Coat		

\* Data From Control Panel In Cleaning Ability Demonstration Test



**GENCORP  
AÉROJET  
ASRM Division**

*Task 2A - Cleaning Ability Test (Cont'd)*

## **Results Of Compatibility Characterization**

- Agents Compatible With SemeTel Coating
- Bare Aluminum Requires More Testing (Turco Best)
  - Light To Heavy Smutting Caused By Agents
- TSA Coatings Were Adversely Affected
  - Surface Discoloration And Apparent Coating Loss And Rinse Water Which Over Time Caused Underlying Steel To Develop Corrosion



GENCORP  
AÉROJET  
ASRM Division

### Task 2A - Cleaning Ability Test (Cont'd)

## Cleaning Ability Demonstration

- Purpose: To Demonstrate Ability To Clean HD-2 Grease
- Results:

### Agent

### Turco 3878 LF-NC

- Cleaning Progressed Significantly Entire 30 Minutes
- HP9-4-.30 And SermeTel Panels Cleaned Except Holes In Panels Retained Grease
- TSA Panels Retained Grease In Pores And Surface

### Blue Gold

- Cleaning Progressed Entire 30 Minutes
- HP9-4-.30 And SermeTel Panels Retained Visible Grease Over Surface And In Holes
- TSA Panels Retained Grease In Pores And Surface

### Daraclean 283

- Cleaning Progressed Significantly Entire 30 Minutes
- HP9-4-.30 And SermeTel Panels Cleaned Except Holes In Panels Retained Grease
- TSA Panels Retained Grease In Pores And Surface



GENCORP  
AEROJET  
ASRM Division

*Task 2A - Cleaning Ability Test (Cont'd)*

## Results

### Cleaning Ability Demonstration

- Three Agents Continued Cleaning 30 Minutes
  - Blue Gold Less Vigorously
- Turco And Daraclean Removed Surface Grease (Except TSA Coated Steel)
  - Blue Gold Failed
- Clumps Of Grease In Panel Holes Were Not Removed By Any Agents

\*



GENCORP  
AEROJET  
ASRM Division

Task 2A - Cleaning Ability Test (Cont'd)

## Bonding Demonstration

- Purpose: To Demonstrate Bonding Strength
  - HPG-4-.30 Test Panels
  - Contaminant Was Conoco HD-2 Grease
  - Bond In Tension Testing (Chemlok 205 Primer - Chemlok 236A Adhesive - Kevlar Filled Insulation)
- Results:
  - All Samples Failed Cohesively In Insulation
  - Turco 3878 LF-NC Slightly Higher Strength Than Others
  - Test Data Summary:

Agent	Mean Stress At Peak (PSI)
Turco 3878 LF-NC	423
Blue Gold	412
Daraclean 283	406



GenCorp  
AEROJET  
ASMD/MSL

## Agent Selection

# Task 2B - Case Cleaning Ability

- Purpose: To Verify Turco 3878 LF-NC Able To Clean All Expected Potential Contaminants

- Success Criteria: To Remove Contaminants To Levels That Do Not Interfere With Specification Bond Strength

### • List Of Contaminants:

- Conoco HD-2 Grease
- Hydraulic Fluid
- Corrosion Inhibitors:
  - Sodium Molybdate
  - Sodium Nitrite
  - Sodium Borate
  - Tolytriazole
- Shop Marker Grease Pencil
- Trimsol Cutting Fluid
- Fingerprints
- Bugs Organic Residue
- Zinc Chromate Residue
- Nylon Residue
- Plastic Blast Media residue
- Volatile Corrosion Inhibitor Residue
- Camuba Wax (Tool Coating)
- Bird Droppings
- Trichlor Slurry
- +Hydrocarbon Soot
- Road Dirt
- Shop Dirt
- EPDM Rubber Residue
- Thermal Protection Residue



**GENCORP  
AÉROJET**  
ASRM Division

### Task 2B - Case Cleaning Ability (Cont'd)

## Task 2B Results

<u>Particulate (Mg)</u>	<u>NVR (Mg)</u>	<u>*Mean OSEE</u>	<u>Bond Strength</u>
			<u>Button Pull Mean Stress At Peak (PSI)</u>
Control	0.1	1.1	427
Fingerprints	0.1	1.3	Degraded
Hydraul Fluid	0.2	1.0	Improved
Cutting Fluid	0.5	0.7	Degraded
Grease Pencil	0.6	0.7	Degraded
Bugs	0.5	1.0	Degraded
Zn Chromate	0.3	0.6	Improved
Corr Inhibitors	0.2	0.6	Degraded
Na Moly	0.5	1.1	Degraded
Nylon Residue	0.5	2.5	Degraded
Plastic Blast	0.5	1.0	Degraded
VCI Film	0.5	0.7	Improved
Carnauba Wax	0.3	0.9	Degraded
Bird Droppings	0.3	0.6	Degraded
Trichlor Slurry	0.5	0.5	Degraded
HD-2 Grease	0.3	1.0	Degraded

\*Comparison of OSEE Readings  
Before Contamination Applied  
And After Contamination Cleaned Off



**GENCORP  
AEROCET  
ASAM Division**

**Task 2B - Case Cleaning Ability (Cont'd)**

## **Task 2B Results (Cont'd)**

- Adequate Bond Strength Demonstrated For Turco 3878 LF-NC
- All Contaminants Removed Sufficiently
- All Samples Failed Cohesively In Rubber
- Small Bond Strength Variation Considering Diversity Of Contaminants
- Chemlok Bonding Ability Must Be Factor



GENCORP  
AÉROJET  
ASRM Division

*Agent Selection*

## Turco 3878 LF-NC Selected

- Best Results Over Other Two Agents In
  - Compatibility Characterization Testing
  - Bonding Demonstration
- Co-Winner With Daraclean 283 In HD-2 Grease Cleaning Ability Demonstration
- Co-Winner With Blue Gold In Residual Species Analysis
- Demonstrated Ability To Remove Wide Variety Of Potential ASRM Contaminants



**GENCORP  
AÉROJET**  
ASFM Division

*Process Optimization*

## **Task 3 - Process Optimization**

- Purpose: To Evaluate The Sensitivity Of The Aqueous Cleaning Process To Changes In Parameters That Control The Process
- Taguchi Matrix Utilized
- Success Criteria: Identify Preliminary Target Process Settings And Functional Limits (NVR Cleanliness Levels Must Also Be Within Level Previously Demonstrating Successful Bonding)
- Bonding To Be Verified In Task 4 Utilizing Optimized Process Settings
- Task 3 Currently In Progress



GENCORP  
AÉROJET  
ASFM Division

*Task 3 Process Optimization (Cont'd)*

# Taguchi Matrix



GENCORP  
AEROCET  
ASHM Division

## General Observations

- Aqueous Cleaning Appears Effective For Steel And SermeTel Coated Metal
- Aqueous Cleaning Agents Appears Unsuitable For Thermal Spray Aluminum Coatings
- Aqueous Cleaning Agents Apparently Stain And/ Or Attack Bare Aluminum To Various Extents (Effect Not Characterized)
- Aqueous Cleaning Appears To Remove Wide Variety Of Contaminants From Flat Surfaces, But Supplementary Assistance Needed To Remove Tenacious Contaminants From Holes
- Hot Rinse Water Appears To Be Beneficial To Aid Drying To Prevent Rapid Oxidation Of Bare Steel



GENCORP  
AÉROJET  
ASRM Division

## ASRM Aqueous Cleaning Development

### **Summary**

- ASRM Process Development In Aqueous Cleaning Is Progressing Satisfactorily
  - Agent Selected
  - Optimization In Progress
  - Demonstrated At Lab Scale That Aqueous Cleaning Is Effective Alternative To Vapor Degreasing
- *We're Committed To Successful Full-Scale Factory Activation*



## NASA SCIENTIFIC AND TECHNICAL DOCUMENT AVAILABILITY AUTHORIZATION (DAA)

To be initiated by the responsible NASA Project Officer, Technical Monitor, or other appropriate NASA official for all presentations, reports, papers, and proceedings that contain scientific and technical information. Explanations are on the back of this form and are presented in greater detail in NHB 2200.2, "NASA Scientific and Technical Information Handbook."		<input type="checkbox"/> Original <input type="checkbox"/> Modified	(CASI Use Only) Control No Date <u>11-20-92</u>
I. DOCUMENT/PROJECT IDENTIFICATION (Information contained on report documentation page should not be repeated except title, date and contract number)			
Title: <u>ASRM Process Development in Aqueous Cleaning</u>			
Author(s): <u>Bill Swisher</u>			
Originating NASA Organization <u>MSFC</u>			
Performing Organization (if different) <u>Lockheed (Aerojet)</u>			
Contract/Grant/Interagency/Project Number(s) <u>NAS8-37800</u>			
Document Number(s) _____ Document Date _____			
(For presentations or externally published documents, enter appropriate information on the intended publication such as name, place, and date of conference, periodical or journal title, or book title and publisher: <u>JANNAF Interagency Committee, Rocket Nozzle Technology Sub-Committee, Sunnyvale, CA, December 8-10, 1992</u> )			
These documents must be routed to NASA Headquarters, International Affairs Division for approval. (See Section VII))			
II. AVAILABILITY CATEGORY			
Check the appropriate category(ies):			
Security Classification: <input type="checkbox"/> Secret <input type="checkbox"/> Secret RD <input type="checkbox"/> Confidential <input type="checkbox"/> Confidential RD <input checked="" type="checkbox"/> Unclassified			
Export Controlled Document - Documents marked in this block must be routed to NASA Headquarters International Affairs Division for approval.			
<input type="checkbox"/> ITAR <input type="checkbox"/> EAR			
NASA Restricted Distribution Document			
<input type="checkbox"/> FEDD <input type="checkbox"/> Limited Distribution <input type="checkbox"/> Special Conditions-See Section III			
Document disclosing an invention			
<input type="checkbox"/> Documents marked in this block must be withheld from release until six months have elapsed after submission of this form, unless a different release date is established by the appropriate counsel. (See Section IX).			
Publicly Available Document			
<input type="checkbox"/> Publicly available documents must be unclassified and may not be export-controlled or restricted distribution documents.			
<input type="checkbox"/> Copyrighted <input type="checkbox"/> Not copyrighted Conc: <u>SA01/A. A. McCool</u>			
P.26			
III. SPECIAL CONDITIONS			
Check one or more of the applicable boxes in each of (a) and (b) as the basis for special restricted distribution if the "Special Conditions" box under NASA Restricted Distribution Document in Section II is checked. Guidelines are provided on reverse side of form.			
a. This document contains:			
<input type="checkbox"/> Foreign government information <input type="checkbox"/> Commercial product test or evaluation results <input type="checkbox"/> Preliminary information <input type="checkbox"/> Information subject to special contract provision			
<input type="checkbox"/> Other-Specify _____			
b. Check one of the following limitations as appropriate:			
<input type="checkbox"/> U.S. Government agencies and U.S. Government agency contractors only <input type="checkbox"/> NASA contractors and U.S. Government agencies only <input type="checkbox"/> U.S. Government agencies only			
<input type="checkbox"/> NASA personnel and NASA contractors only <input type="checkbox"/> NASA personnel only <input type="checkbox"/> Available only with approval of issuing office, _____			
IV. BLANKET RELEASE (OPTIONAL)			
All documents issued under the following contract/grant/project number _____ may be processed as checked in Sections II and III.			
The blanket release authorization granted _____ is: _____			
<input type="checkbox"/> Rescinded - Future documents must have individual availability authorizations. <input type="checkbox"/> Modified - Limitations for all documents processed in the STI system under the blanket release should be changed to conform to blocks as checked in Section II.			
V. PROJECT OFFICER/TECHNICAL MONITOR			
<u>Royce Mitchell</u> <u>SA61</u> <u>R. Mitchell</u> <u>11/23/92</u>			
Typed Name of Project Officer/Technical Monitor Office Code Signature Date			
VI. PROGRAM OFFICE REVIEW <input type="checkbox"/> Approved <input type="checkbox"/> Not Approved			
<u>Russell Bardos</u> <u>DL</u> Program Office and Code Signature Date			
Typed Name of Program Office Representative			
VII. INTERNATIONAL AFFAIRS DIVISION REVIEW			
<input type="checkbox"/> Open, domestic conference presentation approved. <input type="checkbox"/> Export controlled limitation is not applicable.			
<input type="checkbox"/> Foreign publication/presentation approved. <input type="checkbox"/> The following Export controlled limitation (ITAR/EAR) is assigned to this document: _____			
<input type="checkbox"/> Export controlled limitation is approved.			
International Affairs Div. Representative Title Date			
VIII. EXPIRATION OF REVIEW TIME			
The document is being released in accordance with the availability category and limitation checked in Section II since no objection was received from the Program Office within 20 days of submission, as specified by NHB 2200.2, and approval by the International Affairs Division is not required.			
Name & Title _____ Office Code _____ Date _____			
Note: This release procedure cannot be used with documents designated as Export Controlled Documents, conference presentations or foreign publications.			
IX. DOCUMENTS DISCLOSING AN INVENTION			
a. This document may be released on _____ Installation Patent or Intellectual Property Counsel _____ Date _____			
b. The document was processed on _____ in accordance with Sections II and III as applicable. NASA CASI _____ Date _____			





